

62

AD-A202 544



ROYAL AEROSPACE ESTABLISHMENT

DEFORMATION OF Ti-6Al-4V BAR AND EXTRUSION
UNDER SUPERPLASTIC FORMING CONDITIONS

by

D. V. Dunford
P. G. Partridge

July 1988

DTIC
ELECTE
22 JAN 1989
S
E

Procurement Executive, Ministry of Defence
Farnborough, Hants

89 1 19 053
UNLIMITED



ROYAL AEROSPACE ESTABLISHMENT

Technical Memorandum Mat/Str 1110

Received for printing 29 July 1988

DEFORMATION OF Ti-6Al-4V BAR AND EXTRUSION
UNDER SUPERPLASTIC FORMING CONDITIONS

by

D. V. Dunford

P. G. Partridge

Accession For

NTIS GRAB

DTIC TAB

Unannounced

Justification

By

Distribution/

Availability Codes

Dist

Avail and/or

Special

A-1

SUMMARY

There is increasing interest in the use of conventional product forms such as bar and extrusions for superplastic forming (SPF) of pressure vessels and tubular body shells. Tests have been carried out to compare the superplasticity of Ti-6Al-4V bar and extrusion with that reported for sheet. The flow stresses, m-values and plastic anisotropy were measured and related to the microstructure. Resulting anisotropy occurred in specimens machine both parallel (L) and perpendicular (T) to the extrusion major axis. Anisotropy also occurred in specimens machine perpendicular (T), but not parallel (L) to the bar major axis. The anisotropy can be explained in terms of the directionality of the microstructure. It is concluded that for limited strains these conventional product forms, although having non-ideal microstructures can be suitable for superplastic forming of components. *GRAB BTAV. (TES)*

To be presented at the International Conference on Superplasticity and Superplastic forming, Blaine, Washington, USA, 1 to 4 August 1988.

Copyright

©

Controller HMSO London

1988

Introduction

The superplastic forming (SPF) of titanium alloys in sheet form is well established and the emphasis has moved towards optimum processing for particular structures [1], and on the post-formed mechanical properties [2]. Meanwhile the need to reduce costs and weight has directed attention to other product forms such as rolled bar and extruded sections for superplastic forming into bottles or pressure vessels. Previous work on textured rectangular rolled bar [3-4] showed texture had negligible effect but the aligned contiguous α -microstructure caused stress and strain anisotropy during deformation under superplastic conditions. Further tests have been carried out to compare the behaviour of round bar, and of an extruded U-channel section in Ti-6Al-4V alloy under superplastic conditions. The results obtained are described in the paper.

Experimental Details

The Ti-6Al-4V (IMI 318) extruded section (Fig 1) was produced by conventional extrusion at 950°C and had dimensions of 120 mm wide x 18 mm thick in the web section. The rolled bar was 50 mm diameter. Tensile test pieces aligned parallel to the principal orthogonal directions L and T were machined from the web of the extrusion as shown in Fig 1 and from the axis (L) and diameter (T) of the bar; the gauge lengths of test pieces were 20 mm long and 9 mm diameter. Uniaxial tensile tests were carried out at 925°C at strain rates of $3 \times 10^{-4} \text{ s}^{-1}$ (extrusion) and $9 \times 10^{-5} \text{ s}^{-1}$ (bar) to elongations up to 400%. The flow stresses and m-values were determined within the range 4-25% elongation and compared with data reported for IMI 318 sheet [5].

Results

The microstructures of the extruded and bar materials were examined after annealing for 2h at 925°C and cooling at 25°C/minute to simulate the thermal cycle experienced under superplastic conditions. The microstructures are shown in Figs 2a and 3a. The α -phase dimensions varied up to 16 μm in the L-direction with the α -phase contiguous and aligned in this direction. The α -phase dimensions were generally much less in the T-directions. The microstructures after deformation to strains of 2.24 (bar) and 1.2 (extrusion) are shown in Fig 2b and 3b; the microstructure was much less aligned and the α -phase appeared to be more equiaxed and broken up into isolated grains.

The shape of the cross-sections in the test piece gauge lengths after deformation to area strains of 2.07-2.24 are shown for the bar in Fig 4; a circular cross-section was obtained for the L-oriented test piece and an elliptical cross-section for the T-oriented test piece, with the maximum diameter parallel to the T-direction. The corresponding cross-section for the extruded material after deformation to strains of 1.2-1.36 is shown in Fig 4; for both L and T orientation test pieces the cross-sections become elliptical during deformation, with the maximum diameter in the T-direction (L oriented test piece) and the L-direction (T oriented test piece). The elliptical shaped cross-section indicated a resistance to deformation in the direction of the larger diameter compared with the orthogonal direction. In all cases the maximum diameter was parallel to the direction of the aligned microstructure in the initial bar and extrusion.

The flow stress v strain rate curves for the extrusion and bar L-oriented test pieces are shown in Fig 5. Over the whole strain rate range the flow stresses were in the order $\sigma_f \text{ extrusion} > \sigma_f \text{ bar} > \sigma_f \text{ sheet}$. The corresponding m-values v strain rate curves are plotted in Fig 6. The coarser microstructure in the bar and extrusion caused a shift in the peaks of the curves to lower strain rates compared with the curve for sheet. The extruded material

also showed a sharper peak compared with the other materials. Although for extrusions the uniaxial tests were carried out at strain rates corresponding to maximum m -value for the sheet ($3 \times 10^{-4} \text{ s}^{-1}$) whilst the bar was tested at a lower strain rate ($9 \times 10^{-5} \text{ s}^{-1}$) which gave a similar m -value to that of sheet ($m > 0.70$); anisotropic deformation occurred for bar and extrusion under both test conditions.

Discussion and Conclusions

The results show that for bar and extrusions high m -values and low flow stresses can be obtained with microstructures which were not ideal for superplasticity. To obtain the same flow stress as used for superplastic sheet, with $m > 0.6$ the ratio of the strain rates ($\dot{\epsilon}$) would be $\dot{\epsilon}_{\text{sheet}} : \dot{\epsilon}_{\text{bar}} : \dot{\epsilon}_{\text{extrusion}} = 2.4 : 2.1 : 1$. A fivefold increase in forming time for the extruded material is likely to impose a severe cost penalty on processing. The other characteristic of the bar and extruded material was the tendency to deform anisotropically under superplastic conditions. This behaviour has also been reported in thin sheet test pieces when the microstructure was strongly aligned [6]. This is illustrated in Fig 7 for sheet test pieces machined from rolled bar [6] the non-uniform deformation in Fig 7a was caused by the banding shown in Fig 7b; note the minimum transverse strain occurred at the position of the aligned microstructure at A. This behaviour has been explained in terms of the resistance to sliding in α/α phase grain boundaries compared with β/β grain boundaries [3,4,7].

Although isotropic strain and high m -values can be obtained in conventionally processed material in a particular direction of stressing, eg rolled bar in the L-direction, for more homogeneous deformation at higher strain rates some modification to the rolling, extrusion or heat treatment operations will be required. This may involve some cost increases in exchange for subsequent reduced component manufacturing costs by SPF.

References

1. D. Stephen, Designing with Titanium, Inst.Metals, (1986), 108
2. P. G. Partridge et al, Superplasticity, AGARD Lecture Series No 154, (1987), 6
3. D. S. McDarmaid et al, J.Mater.Sci., 19, (1984), 2378
4. D. S. McDarmaid et al, J.Mater.Sci., 20, (1985), 1976
5. C. D. Ingelbrecht, Designing with Titanium, Inst.Metals, (1986), 252
6. C. D. Ingelbrecht, P. G. Partridge, J.Mater.Sci., 21, (1986), 4071
7. P. G. Partridge et al, Acta Met., 33, (1985), 571

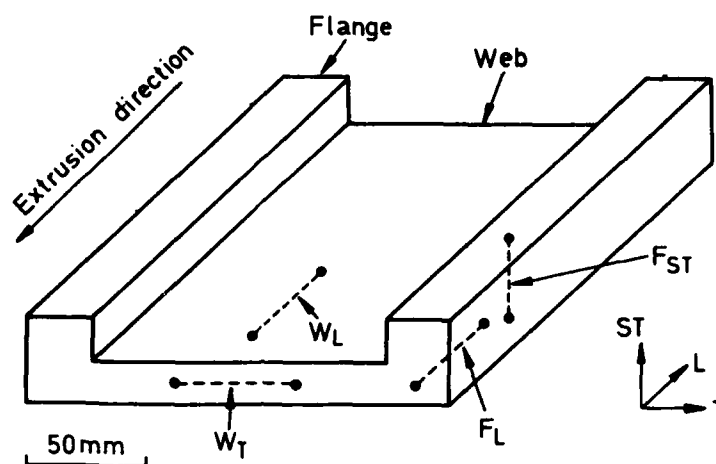


Fig 1 Position of test piece in extruded section

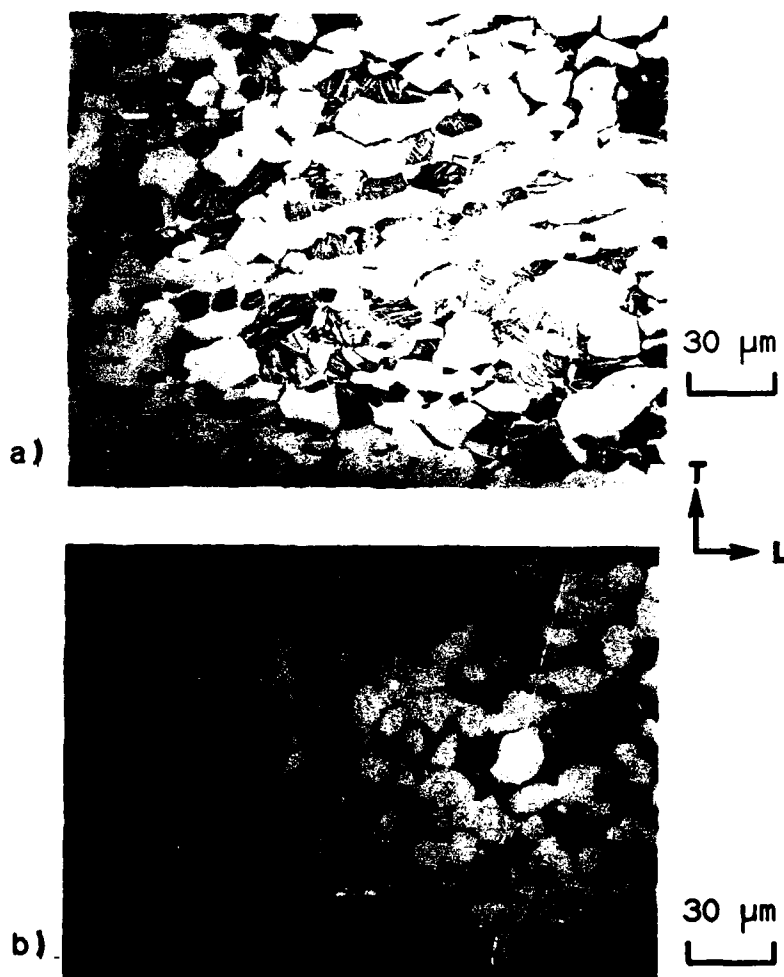


Fig 2 Microstructures of IMI 318 bar (a) after thermal cycle, (b) after superplastic strain (area strain, $\bar{\epsilon} = 2.24$)

Figs 3-5


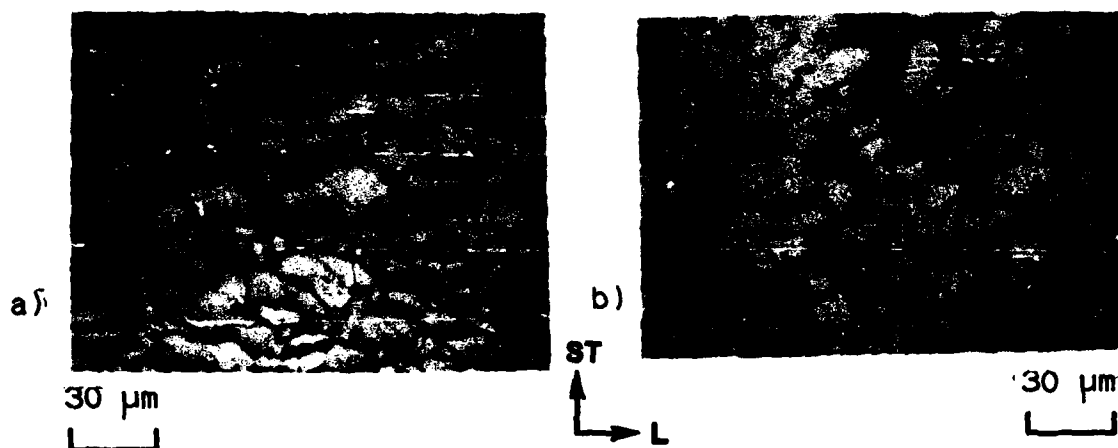


Fig 3 Microstructures of IMI 318 extrusion, W_T test piece
(a) after thermal cycle, (b) after superplastic strain
(area strain, $\bar{\epsilon} = 1.20$)

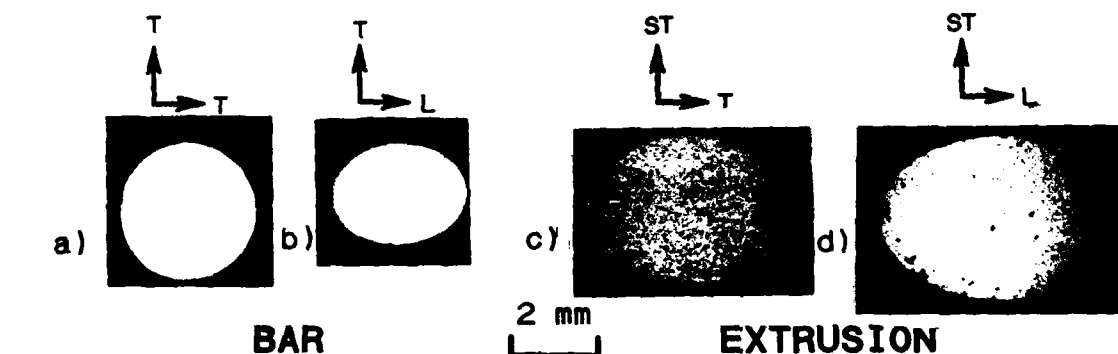

$\bar{\epsilon}$	2.07	2.24	1.36	1.20
$\frac{d_{min}}{d_{max}}$	1.0	0.74	0.68	0.69

Fig 4 Cross-sections after deformation. Round bar
(a) L-direction, (b) T-direction and extrusion
(c) W_T test piece, (d) W_T test piece. Minimum
diameter, d_{min} , maximum diameter, d_{max}

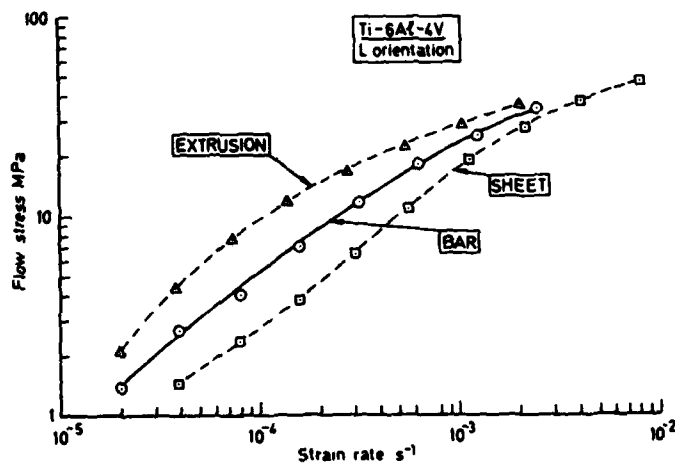


Fig 5 Flow stress v strain rate for IMI 318 bar,
extrusion and sheet at 925°C

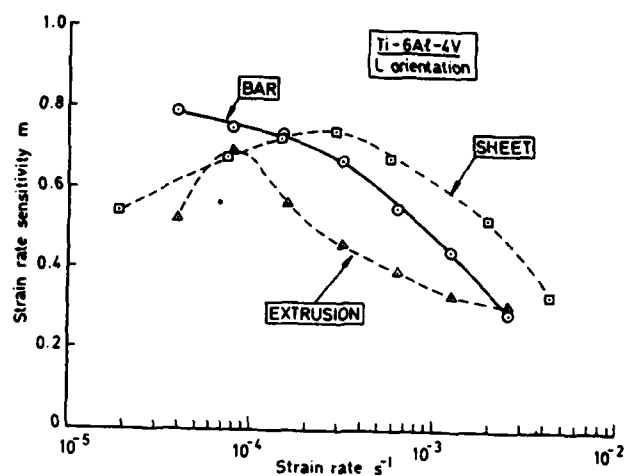


Fig 6 m -values v strain rate for IMI 318 bar, extrusion and sheet at 925°C

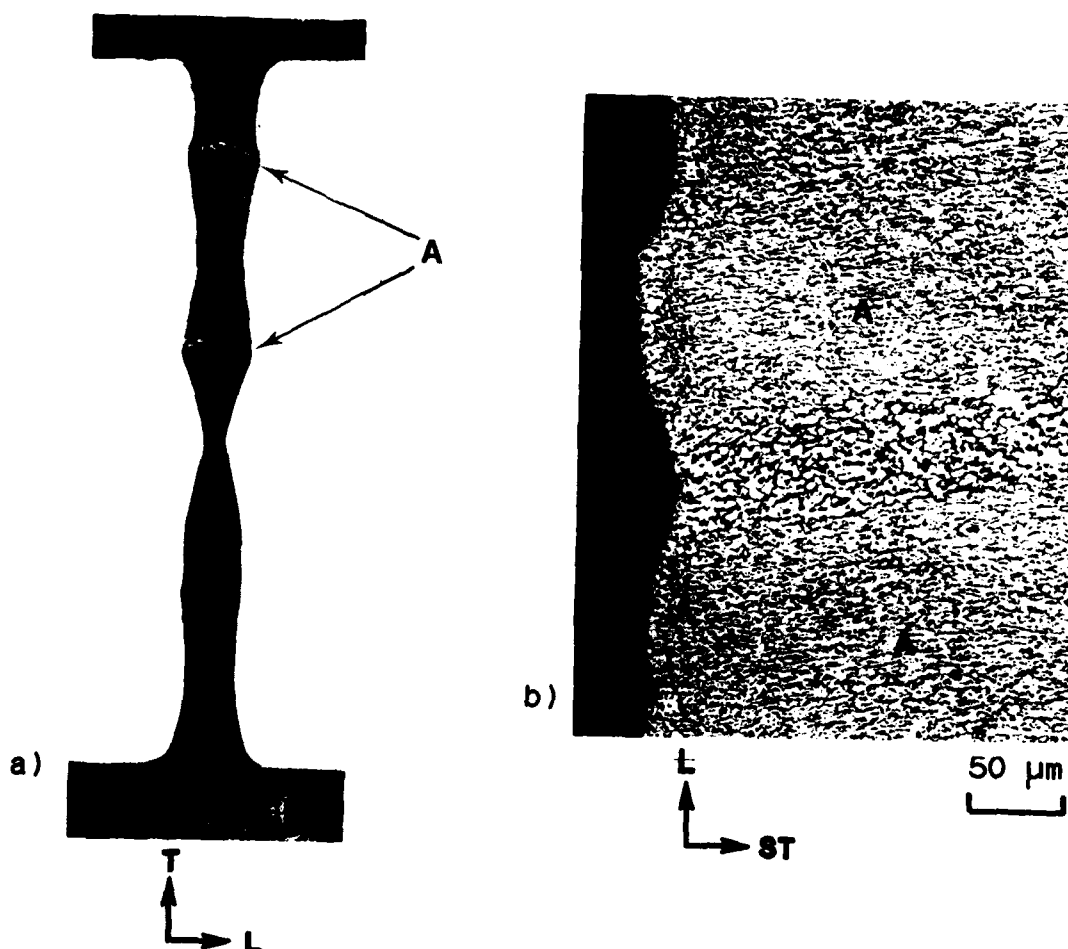


Fig 7 Ti-6Al-4V sheet machined from bar (a) test piece, (b) microstructure, after 273% extension at 875°C, $\dot{\epsilon} = 3 \times 10^{-4}$

REPORT DOCUMENTATION PAGE

Overall security classification of this page

UNLIMITED

As far as possible this page should contain only unclassified information. If it is necessary to enter classified information, the box above must be marked to indicate the classification, e.g. Restricted, Confidential or Secret.

1. DRIC Reference (to be added by DRIC)	2. Originator's Reference RAE TM Mat/Str 1110	3. Agency Reference	4. Report Security Classification/Marking UNLIMITED		
5. DRIC Code for Originator 7673000W	6. Originator (Corporate Author) Name and Location Royal Aerospace Establishment, Farnborough, Hants, UK				
5a. Sponsoring Agency's Code	6a. Sponsoring Agency (Contract Authority) Name and Location				
7. Title Deformation of Ti-6Al-4V bar and extrusion under superplastic forming conditions					
7a. (For Translations) Title in Foreign Language					
7b. (For Conference Papers) Title, Place and Date of Conference					
8. Author 1. Surname, Initials Dunford, D.V.	9a. Author 2 Partridge, P.G.	9b. Authors 3, 4		10. Date July 1988	Pages 6
				Refs. 7	
11. Contract Number	12. Period	13. Project		14. Other Reference Nos.	
15. Distribution statement (a) Controlled by Head Materials & Structures Dept (b) Special limitations (if any) - If it is intended that a copy of this document shall be released overseas refer to RAE Leaflet No.3 to Supplement 6 of MOD Manual 4.					
16. Descriptors (Keywords) (Descriptors marked * are selected from TEST) Titanium alloy. Superplastic deformation. Bar. Extrusion. Sheet.					
17. Abstract There is increasing interest in the use of conventional product forms such as bar and extrusions for superplastic forming (SPF) of pressure vessels and tubular body shells. Tests have been carried out to compare the superplasticity of Ti-6Al-4V bar and extrusion with that reported for sheet. The flow stresses, m-values and plastic anisotropy were measured and related to the microstructure. Resulting anisotropy occurred in specimens machine both parallel (L) and perpendicular (T) to the extrusion major axis. Anisotropy also occurred in specimens machine perpendicular (T), but not parallel (L) to the bar major axis. The anisotropy can be explained in terms of the directionality of the microstructure. It is concluded that for limited strains these conventional product forms, although having non-ideal microstructures can be suitable for superplastic forming of components.					

10201